



Razi Applied Science Foundation

Test Report

Inspection Certificate 3.1 (EN 10204)

Website: www.razi-foundation.com

Email: info@razi-foundation.com

No. 27, Fernan St., Shahid Ghasem Asghari Blvd., Km 21 Karadj Makhsoos Road, Tehran, Iran Tel: (+9821) 49732 , 46841121 , Fax: (+9821) 49732

Client:Arma

Address:Tehran

Sample Name:Bullet 2

Contract No.	2-34326
Date Reported	2020-02-12
Revision No.	0
Attachment	
Sample Received on	2020-01-26
Tested On	2020-01-27
Client Letter No	
Client Letter Date	

Environmental Conditions:

Temperature

Humidity:

Sampling was performed by the client

Page No 1

Of 6
Accredited by

As Na Li + Ca

ISO/IEC 17025
Analitica/ ILAC
No : AAC.A.00223

NACI
National Accreditation
Center of IRAN
Cert No. T/3048



Laboratory Manager:

S.Nasiri

Technical Manager:

R.Khoshmanesh



For Information Purpose Only

■Samples will be retained for a period of one month only, unless otherwise requested. ■RASf is not responsible for compliance of sample name with the tested sample. ■The test results relate only to the samples tested. ■This report shall only be reproduced in full. Approval of the testing laboratory is required for reproduction. ■Report are invalid without hologram.

Hologram
Place



Razi Applied Science Foundation

Test Report

Inspection Certificate 3.1 (EN 10204)

Website: www.razi-foundation.com

Email: info@razi-foundation.com

No. 27, Fernan St., Shahid Ghasem Asghari Blvd., Km 21 Karadj Makhsoos Road, Tehran, Iran Tel: (+9821) 49732 , 46841121 , Fax: (+9821) 49732

Client:Arma

Address:Tehran

Sample Name:Bullet 2

Environmental Conditions:

Temperature 22C

Humidity: %24

Sampling was performed by the client

Page No 2

Of 6
Accredited by

Chemical Analysis by Atomic Emission Spectrometry (OES)

Standard Test Method: --

INSTRUMENT: OXFORD☒ ARL☐ HITACHI☐

Preparation Sample: Grinding☒ Remelting And grinding (ASTM E1010-16)☐ Machining☐

Material Type: Ferrous☒ Non Ferrous☐

Result of chemical analysis test:

C	Si	Mn	P	S	Cr	Mo	Ni	Cu	Nb	V	Fe
3.03	0.63	0.43	0.013	0.018	11.05	0.02	0.12	0.03	< 0.005	< 0.005	Base

As-Nal-Ti-Ga

ISO/IEC 17025
Analitica/ ILAC
No : AAC.A.00223

NACI
National Accreditation
Center of IRAN
Cert No. T/3048



Laboratory Manager:

S.Nasiri

Technical Manager:

R.Khoshmanesh

For Information Purpose Only

■Samples will be retained for a period of one month only, unless otherwise requested. ■RASf is not responsible for compliance of sample name with the tested sample. ■The test results relate only to the samples tested. ■This report shall only be reproduced in full. Approval of the testing laboratory is required for reproduction. ■Report are invalid without hologram.

Hologram
Place



Razi Applied Science Foundation

Test Report

Inspection Certificate 3.1 (EN 10204)

Website: www.razi-foundation.com

Email: info@razi-foundation.com

No. 27, Fernan St., Shahid Ghasem Asghari Blvd., Km 21 Karadj Makhsoos Road, Tehran, Iran Tel: (+9821) 49732 , 46841121 , Fax: (+9821) 49732

Client:Arma

Address:Tehran

Sample Name:Bullet 2

Environmental Conditions: Temperature 25C Humidity: %41 Sampling was performed by the client Page No 3

Of 6
Accredited by

As-Nalita-Ga

ISO/IEC 17025
Analitica/ ILAC
No : AAC.A.00223

NACI
National Accreditation
Center of IRAN
Cert No. T/3048



Laboratory Manager:

S.Nasiri

Technical Manager:

R.Khoshmanesh

Rockwell C HARDNESS TESTING

Reference Standard: ASTM E18(2017) - BS EN ISO 6508-1(2015)

Instrument: INNOVATEST NEXUS 8000XL

Indenter ☒Diamond sphero-conical indenter ☐ball 1/16-in. (1.588-mm)

Applied Force: ☐HRA 60 Kgf (588.4 N) ☐HRB 100 Kgf (980.07 N) ☒HRC 150 Kgf (1471 N)

No.	Test location	Hardness at measured point(HRC)			Hardness (mean) HRC	Acceptance limit HRC	Uncertainty
		Point 1	Point 2	Point 3			
1	Center	59	60	60	60	---	---

For Information Purpose Only

■Samples will be retained for a period of one month only, unless otherwise requested. ■RASf is not responsible for compliance of sample name with the tested sample. ■The test results relate only to the samples tested. ■This report shall only be reproduced in full. Approval of the testing laboratory is required for reproduction. ■Report are invalid without hologram.

Hologram
Place



Razi Applied Science Foundation

Test Report

Inspection Certificate 3.1 (EN 10204)

Website: www.razi-foundation.com

Email: info@razi-foundation.com

No. 27, Fernan St., Shahid Ghasem Asghari Blvd., Km 21 Karadj Makhsous Road, Tehran, Iran Tel: (+9821) 49732 , 46841121 , Fax: (+9821) 49732

Client:Arma

Address:Tehran

Sample Name:Bullet 2

Environmental Conditions:

Temperature 25C

Humidity: %41

Sampling was performed by the client

Page No 4

Of 6
Accredited by

AsNaLiTiCa

ISO/IEC 17025
Analitica/ ILAC
No : AAC.A.00223

NACI
National Accreditation
Center of IRAN
Cert No. T/3048



Laboratory Manager:

S.Nasiri

Technical Manager:

R.Khoshmanesh

Microstructure

Ref. Standards: ASTM E3-11 Sample Preparation of Metallographic specimen

ASTM E 407-07 Microetching of Metals

ASTM E 883-11 Metallographic Photomicrography

Microstructure (after etching)

The inter-dendritic network of iron-chromium carbide and the dendritic pattern of martensite and precipitation of fine Cr_{23}C_6 carbide within martensitic matrix.

Remarks: ---

Micrographs of sample are shown in figure 1 to 2.

For Information Purpose Only

■Samples will be retained for a period of one month only, unless otherwise requested. ■RASf is not responsible for compliance of sample name with the tested sample. ■The test results relate only to the samples tested. ■This report shall only be reproduced in full. Approval of the testing laboratory is required for reproduction. ■Report are invalid without hologram.

Hologram
Place



Razi Applied Science Foundation

Test Report

Inspection Certificate 3.1 (EN 10204)

Website: www.razi-foundation.com

Email: info@razi-foundation.com

No. 27, Fernan St., Shahid Ghasem Asghari Blvd., Km 21 Karadj Makhsoos Road, Tehran, Iran Tel: (+9821) 49732 , 46841121 , Fax: (+9821) 49732

Client:Arma


Address:Tehran

Sample Name:Bullet 2

Contract No.	2-34326
Date Reported	2020-02-10
Revision No.	0
Attachment	
Sample Received on	2020-01-26
Tested On	2020-01-27
Client Letter No	
Client Letter Date	

Environmental Conditions: Temperature 25C Humidity: %41 Sampling was performed by the client Page No 5

Fig 1. The inter-dendritic network of iron-chromium carbide (white) and the dendritic pattern of martensite (gray).
Mag. 100X
Etch Solution: Nital %2

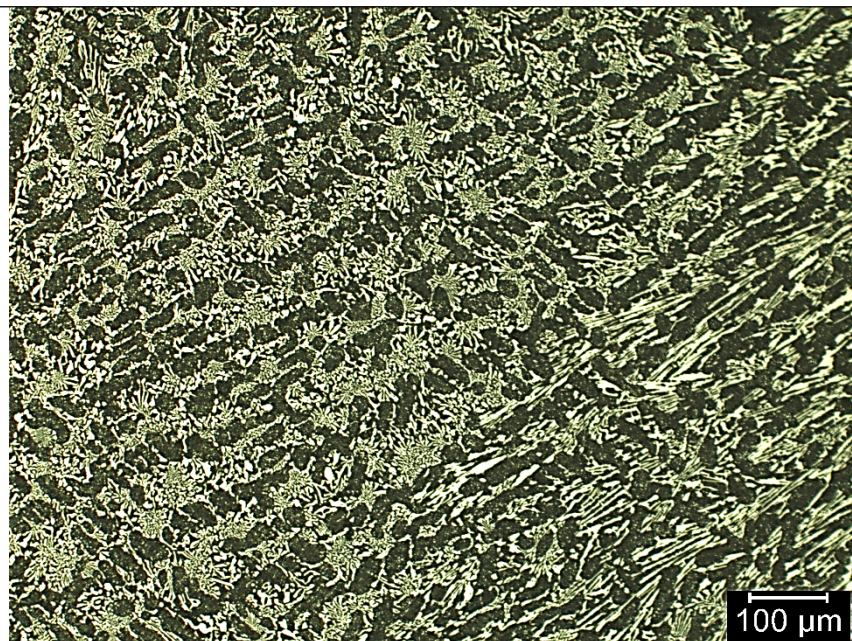

Of 6
Accredited by

As Na Li + Ca

ISO/IEC 17025
Analitica/ ILAC
No : AAC.A.00223

NACI
National Accreditation
Center of IRAN
Cert No. T/3048



Laboratory Manager:

S.Nasiri

Technical Manager:

R.Khoshmanesh

For Information Purpose Only

■Samples will be retained for a period of one month only, unless otherwise requested. ■RASf is not responsible for compliance of sample name with the tested sample. ■The test results relate only to the samples tested. ■This report shall only be reproduced in full. Approval of the testing laboratory is required for reproduction. ■Report are invalid without hologram.

Hologram
Place



Razi Applied Science Foundation

Test Report

Inspection Certificate 3.1 (EN 10204)

Website: www.razi-foundation.com

Email: info@razi-foundation.com

No. 27, Fernan St., Shahid Ghasem Asghari Blvd., Km 21 Karadj Makhsous Road, Tehran, Iran Tel: (+9821) 49732 , 46841121 , Fax: (+9821) 49732

Client:Arma

Address:Tehran

Sample Name:Bullet 2

Contract No.	2-34326
Date Reported	2020-02-10
Revision No.	0
Attachment	
Sample Received on	2020-01-26
Tested On	2020-01-27
Client Letter No	
Client Letter Date	

Environmental Conditions:

Temperature 25C

Humidity: %41

Sampling was performed by the client


Page No 6

Of 6
Accredited by

Fig 2. . Same structure at a higher magnification and precipitation of fine Cr_{23}C_6 carbide within martensitic matrix.

Mag. 500X

Etch Solution: Nital %2

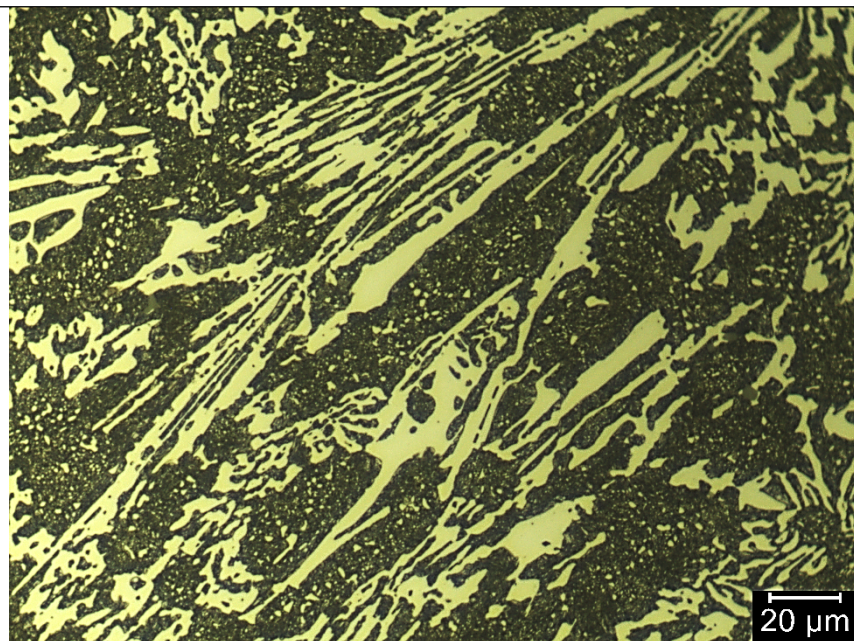

As-Nal-Ti-Ga

ISO/IEC 17025
Analitica/ ILAC
No : AAC.A.00223

NACI
National Accreditation
Center of IRAN
Cert No. T/3048



Laboratory Manager:

S.Nasiri

Technical Manager:

R.Khoshmanesh

For Information Purpose Only

■Samples will be retained for a period of one month only, unless otherwise requested. ■RASf is not responsible for compliance of sample name with the tested sample. ■The test results relate only to the samples tested. ■This report shall only be reproduced in full. Approval of the testing laboratory is required for reproduction. ■Report are invalid without hologram.

Hologram
Place