

TEST REPORT



Razi Applied Science Foundation

In The Name of God

www.razi-foundation.com
info@razi-foundation.com

Contract No.	7-31365
Date Reported	2020-01-13
Revision No.	0
Attachment	
Sample Received on	2020-01-02
Tested On	2020-01-04
Client Letter No	
Client Letter Date	


No.27, Fernan St., Shahid Ghasem Asghari Blvd., Shahr-e-Qods Entrance, Km 21 Karadj Mahsoud Road, Tehran-IRAN Post Code: 3753145114 Tel:(+9821)49732, (+9821)46841121

Client:Arma

Address:Tehran

Sample Name:R2

Environmental Conditions: Temperature Humidity: Sampling was performed by the client Page No 1 Of 3

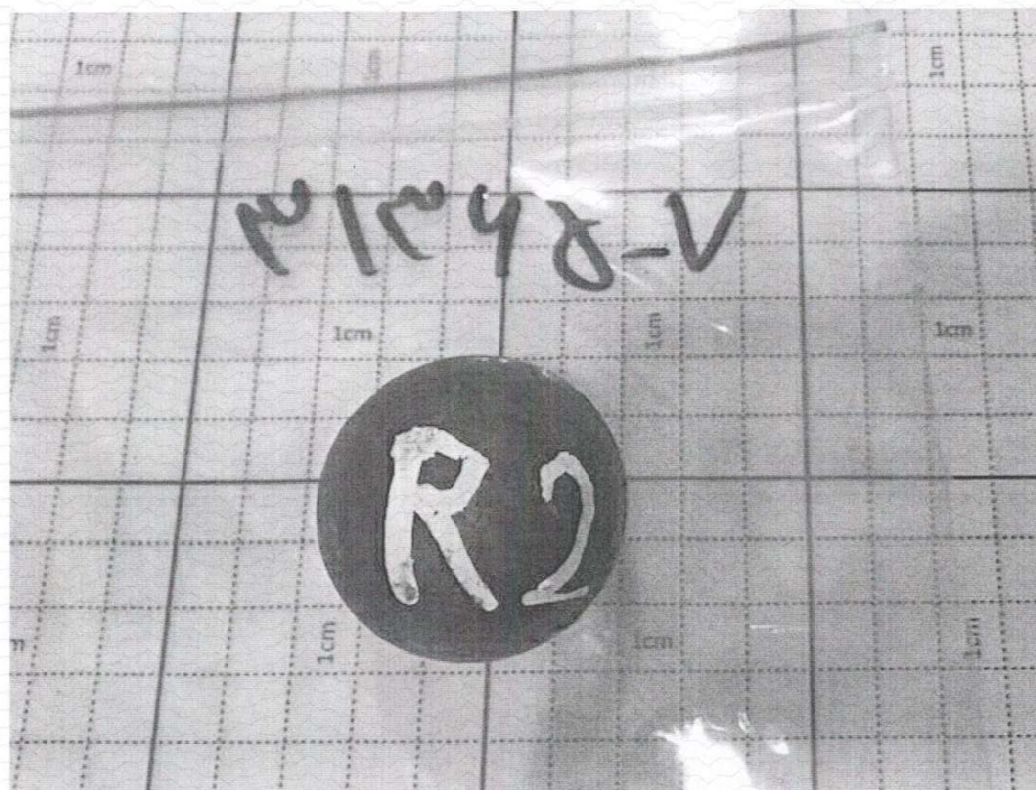

AsNaLaToCa

ILAC FULL MEMBER
ISO/IEC 17025 (2005)

Analitica
Accreditation Certificate
No.AAC.A.00223

Accredited Lab. by:
Institute of Standard & Industrial
Research of Iran T/3048
SAPCO
Mobarakeh Steel Co.
Sazeh Gostar SAIPA
P.O.G.C

Laboratory Manager

S.Nasiri

Technical Manager

R.Khoshmanesh



Razi Applied Science Foundation



- Samples will be retained for a period of one month only, unless otherwise requested.
- Approval of the testing laboratory is required for reproduction.
- The test results relate only to the samples tested.
- RASF is not responsible for compliance of sample name with the tested sample.
- Reports are invalid without hologram & embossed letters.
- This reports shall only be reproduced in full.

TEST REPORT



Razi Applied Science Foundation

In The Name of God

www.razi-foundation.com

info@razi-foundation.com

Contract No.	7-31365
Date Reported	2020-01-13
Revision No.	0
Attachment	
Sample Received on	2020-01-02
Tested On	2020-01-04
Client Letter No	
Client Letter Date	

No.27, Fernan St., Shahid Ghasem Asghari Blvd., Shahr-e-Qods Entrance, Km 21 Karadj Makhsoos Road, Tehran-IRAN Post Code: 3753145114 Tel:(+9821)49732, (+9821)46841121

Client:Arma

Address:Tehran

Sample Name:R2

Environmental Conditions: Temperature 24C Humidity: %20 Sampling was performed by the client Page No 2 Of 3

Chemical Analysis by Atomic Emission Spectrometry (OES)

Standard Test Method: ASTM A751 (2014a)/ ASTM E415(2017)

Standard Practice for Reporting : ASTM E1950 (2017)/ ASTM E29 (2013)

INSTRUMENT: OXFORD ☐ ARL ☐ HITACHI ☒Preparation Sample: Grinding ☒ Remelting And grinding (ASTM E1010-16) ☐ Machining ☐Material Type: Ferrous ☒ Non Ferrous ☐

Result of chemical analysis test:

C	Si	Mn	P	S	Cr	Mo	Ni	Al	Co	Cu	Nb
0.70	0.34	0.86	0.027	0.030	0.52	0.01	0.09	0.006	0.01	0.13	0.002
Ti	V	W	Pb	Sn	B	Zr	Bi	As	Fe		
0.004	0.019	< 0.015	< 0.01	*	< 0.0008	< 0.002	< 0.01	< 0.004	Base		

ILAC FULL MEMBER

ISO/IEC 17025 (2005)

Analitica

Accreditation Certificate

No.AAC.A.00223

Accredited Lab. by:

Institute of Standard & Industrial

Research of Iran T/3048

SAPCO

Mobarakeh Steel Co.

Sazeh Gostar SAIPA

P.O.G.C

Laboratory Manager

S.Nasiri

Technical Manager

R.Khoshmanesh

- Samples will be retained for a period of one month only, unless otherwise requested.
- Approval of the testing laboratory is required for reproduction.
- The test results relate only to the samples tested.
- RASF is not responsible for compliance of sample name with the tested sample.
- Reports are invalid without hologram & embossed letters.
- This reports shall only be reproduced in full.

TEST REPORT



Razi Applied Science Foundation

In The Name of God

www.razi-foundation.com

info@razi-foundation.com

Contract No.	7-31365
Date Reported	2020-01-12
Revision No.	0
Attachment	
Sample Received on	2020-01-02
Tested On	2020-01-04
Client Letter No	
Client Letter Date	

No.27, Fernan St., Shahid Ghasem Asghari Blvd., Shahr-e-Qods Entrance, Km 21 Karadj Makhsoos Road, Tehran-IRAN Post Code: 3753145114 Tel:(+9821)49732, (+9821)46841121

Client:Arma

Address:Tehran

Sample Name:R2

Environmental Conditions: Temperature 25C Humidity: %41 Sampling was performed by the client Page No 3 Of 3

Rockwell C HARDNESS TESTING

Reference Standard: ASTM E18(2017) - BS EN ISO 6508-1(2015)

Instrument: INNOVATEST NEXUS 8000XL

Indenter ☒Diamond sphero-conical indenter ☐ball 1/16-in. (1.588-mm)Applied Force: ☐HRA 60 Kgf (588.4 N) ☐HRB 100 Kgf (980.07 N) ☒HRC 150 Kgf (1471 N)

No.	Test location	Hardness at measured point(HRC)			Hardness (mean) HRC	Acceptance limit HRC	Uncertainty
		Point 1	Point 2	Point 3			
1	Surface	64	64	63	64	---	---
2	0.5 Cm From surface	64	63	63	63	---	---
3	1.0 Cm From surface	64	63	63	63	---	---
4	1.5 Cm From surface	63	63	64	63	---	---
5	2.0 Cm From surface	64	64	63	64	---	---
6	2.5Cm From surface	64	64	64	64	---	---

ILAC FULL MEMBER
ISO/IEC 17025 (2005)Analitica
Accreditation Certificate
No.AAC.A.00223Accredited Lab. by:
Institute of Standard & Industrial
Research of Iran T/3048
SAPCO
Mobarakeh Steel Co.
Sazeh Gostar SAIPA
P.O.G.C

Laboratory Manager

S.Nasiri

Technical Manager

RASF
RAZI
APPLIED SCIENCE
FOUNDATION
K. Khoshmanesh

- Samples will be retained for a period of one month only, unless otherwise requested.
- Approval of the testing laboratory is required for reproduction.
- The test results relate only to the samples tested.
- RASF is not responsible for compliance of sample name with the tested sample.
- Reports are invalid without hologram & embossed letters.
- This reports shall only be reproduced in full.